

# Evaluation of enamel surface roughness after orthodontic bracket debonding with atomic force microscopy

Shadi Mohebi,<sup>a</sup> Hassan-Ali Shafiee,<sup>b</sup> and Nazila Ameli<sup>c</sup>

Urmia, Tehran, and Semnan, Iran

**Introduction:** Achieving a smooth enamel surface after orthodontic bracket debonding is imperative. In this study, we sought to compare the enamel surface roughness values after orthodontic bracket debonding and resin removal using a white stone bur, a tungsten carbide bur, and a tungsten carbide bur under loupe magnification. **Methods:** Thirty sound premolars were randomly divided into 3 groups, and their buccal surfaces were subjected to atomic force microscopy to measure initial surface roughness. Brackets were bonded to the buccal surfaces and debonded after 24 hours. Resin remnants were removed using a white stone bur, a tungsten carbide bur, or a tungsten carbide bur under loupe magnification. The teeth were then subjected to atomic force microscopy again. The time required for composite removal was calculated. Data were analyzed using repeated-measures analysis of variance, 1-way analysis of variance, and the Tukey test. **Results:** Resin removal increased the enamel surface roughness compared with the initial values ( $P < 0.001$ ); however, no significant differences were noted among the 3 groups in this respect after resin removal. The mean times required for smoothing by the tungsten carbide bur and the tungsten carbide bur with a dental loupe were similar ( $P > 0.05$ ); significantly lower than the time with the white stone bur (both,  $P < 0.001$ ). **Conclusions:** The tungsten carbide bur is still recommended for composite removal. (Am J Orthod Dentofacial Orthop 2017;151:521-7)

A major concern when removing orthodontic brackets is restoration of the enamel surface to the pretreatment condition.<sup>1</sup> The quest for an efficient method to remove adhesive resin after debonding of orthodontic brackets has led to the introduction of various techniques and instrumentations.<sup>1,2</sup> Mechanical removal of composite resin includes scraping with a scaler and various burs, such as ultrafine diamond burs, but some believe that they can cause irreversible damage to the enamel.<sup>3,4</sup> Other studies have shown that laser energy may be used for resin removal, since it degrades the resin and reduces the force needed to remove orthodontic attachments. However, the Er:YAG

laser also has been shown to cause irreversible enamel damage.<sup>3</sup>

Using different burs in conjunction with rubber cups and pumice paste seems to be appropriate for resin removal; however, there is a considerable lack of consensus regarding the most efficient route for this.<sup>5,6</sup> Tungsten carbide burs in either a low-speed or a high-speed hand piece have been the method of choice for removing resin remnants.<sup>7,8</sup> Techniques and new composite burs that are less aggressive to the enamel<sup>9</sup> and new instruments such as stone burs, disks, and diamond or silicone coated polishers, also stated to be less aggressive, have been developed.<sup>8</sup> The effect of various rotary instruments on the enamel surface has been assessed qualitatively with scanning electron microscopy.<sup>10-12</sup> However, using quantitative scales enhances the selection of the most efficient method because of the possibility of better assessing and comparing the damage caused by different instruments.<sup>13,14</sup>

The atomic force microscope (AFM) is a scanning probe microscope with biologic applications. It uses a flexible cantilever as a type of spring to measure the force between the tip and the sample. The AFM analysis uses several high-resolution scans and is highly recommended for evaluation of the enamel

<sup>a</sup>Department of Orthodontics, School of Dentistry, Urmia University of Medical Sciences, Urmia, Iran.

<sup>b</sup>Department of Orthodontics, School of Dentistry, Shahid Beheshti University of Medical Sciences, Tehran, Iran.

<sup>c</sup>Department of Orthodontics, School of Dentistry, Semnan University of Medical Sciences, Semnan, Iran.

All authors have completed and submitted the ICMJE Form for Disclosure of Potential Conflicts of Interest, and none were reported.


Address correspondence to: Nazila Ameli, Department of Orthodontics, School of Dentistry, Semnan University of Medical Sciences, 17th Shahrivar blv, Semnan, Iran; e-mail, [Nazilaa.aameli@gmail.com](mailto:Nazilaa.aameli@gmail.com).

Submitted, October 2015; revised and accepted, August 2016.

0889-5406/\$36.00

© 2016 by the American Association of Orthodontists. All rights reserved.

<http://dx.doi.org/10.1016/j.ajodo.2016.08.025>

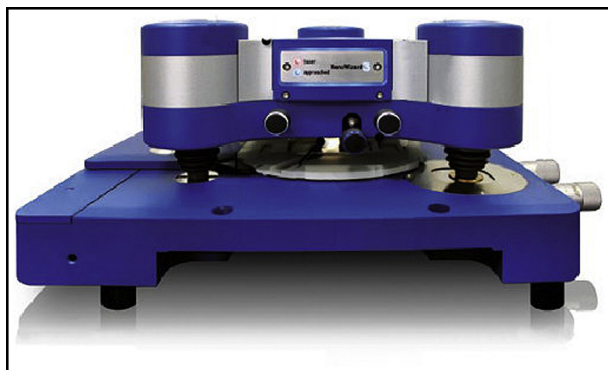

**Fig 1.** AFM core (Nano Wizard II; JPK Instruments, Berlin, Germany).

surface.<sup>15,16</sup> Minimal sample preparation, obtaining 2-dimensional and 3-dimensional images simultaneously and the possibility of reevaluating the sample are among the advantages of this method.<sup>17,18</sup> It has been stated that the use of a dental loupe by the practitioner may affect the quality of the debonding procedure, causing less enamel damage and better resin removal.<sup>19</sup> To date, multiple modalities have been advocated and used to remove adhesive residues after debonding; a large disparity exists in the literature regarding the most efficient way to remove resin after orthodontic treatment. Therefore, we undertook this study to compare the effect of 3 resin removal methods (tungsten carbide bur, white stone bur, and tungsten carbide bur under loupe magnification) on enamel surface roughness assessed by AFM. The time taken for resin removal after bracket debonding was also evaluated.

## MATERIAL AND METHODS

In this in-vitro experimental study, 30 freshly extracted (for orthodontic indications) intact premolars were obtained from 10- to 20-year-old patients. The teeth were stored in distilled water before they were sent to the laboratory and cleaned with a low-speed bristle brush. They were then rinsed with water for 10 seconds and dried with oil-free compressed air. The experimental teeth were mounted in acrylic blocks and stored in isotonic saline solution. The teeth were not sterilized (since sterilization could affect the quality of the bond).<sup>20</sup>

The buccal surface roughness of each tooth was determined by AFM (NanoWizard II; JPK Instruments, Berlin, Germany; Fig 1), equipped with a scanner with a maximum range of  $100 \times 100 \times 5 \mu\text{m}$  in the x, y, and z axes, respectively.




**Fig 2.** Mounted tooth in acrylic block after bonding.

To measure roughness values, the tip of a silicon probe (with a radius of less than 10 nm, height of 4–6  $\mu\text{m}$ , and spring constant of 0.046 N/m) was moved across the middle third of the buccal surface of the samples in the contact mode with  $10^{-6}$  N force. In the contact mode, the tip never left the surface. After obtaining 2 to 3 initial images ( $20 \times 20 \times 5 \mu\text{m}$ ), 5 images of each specimen ( $5 \times 5 \times 5 \mu\text{m}$ ) were extracted from the initial images via blind randomization. Then the teeth were etched for 30 seconds using 37% phosphoric acid gel, rinsed with water, and air dried. The brackets were bonded to the prepared enamel (Reliance Orthodontic Products, Itasca, Ill), excess adhesive was removed, and the resin was light-cured for 40 seconds (Fig 2). All samples were stored in isotonic saline solution at room temperature for 24 hours, and the brackets were debonded with a fine cutter using the peeling method. The teeth were randomly assigned to 3 equal groups with 10 teeth in each group. In the first group, removal of resin remnants was performed with a 12-bladed tungsten carbide bur (0197; D & Z, Frankfurt, Germany) and a low-speed hand piece.

In the second group, a dome-shaped white stone bur (Arkansas 661 DEF; D & Z) in a low-speed hand piece was used for resin removal.

In the third group, removal of resin remnants was performed with a 12-bladed tungsten carbide bur as in the first group, but during the debonding process the operator used a dental loupe (binocular loupe, HR 2.5  $\times$  420 mm; Heine, Dover, NH). All bonding and debonding processes were done by the same operator.

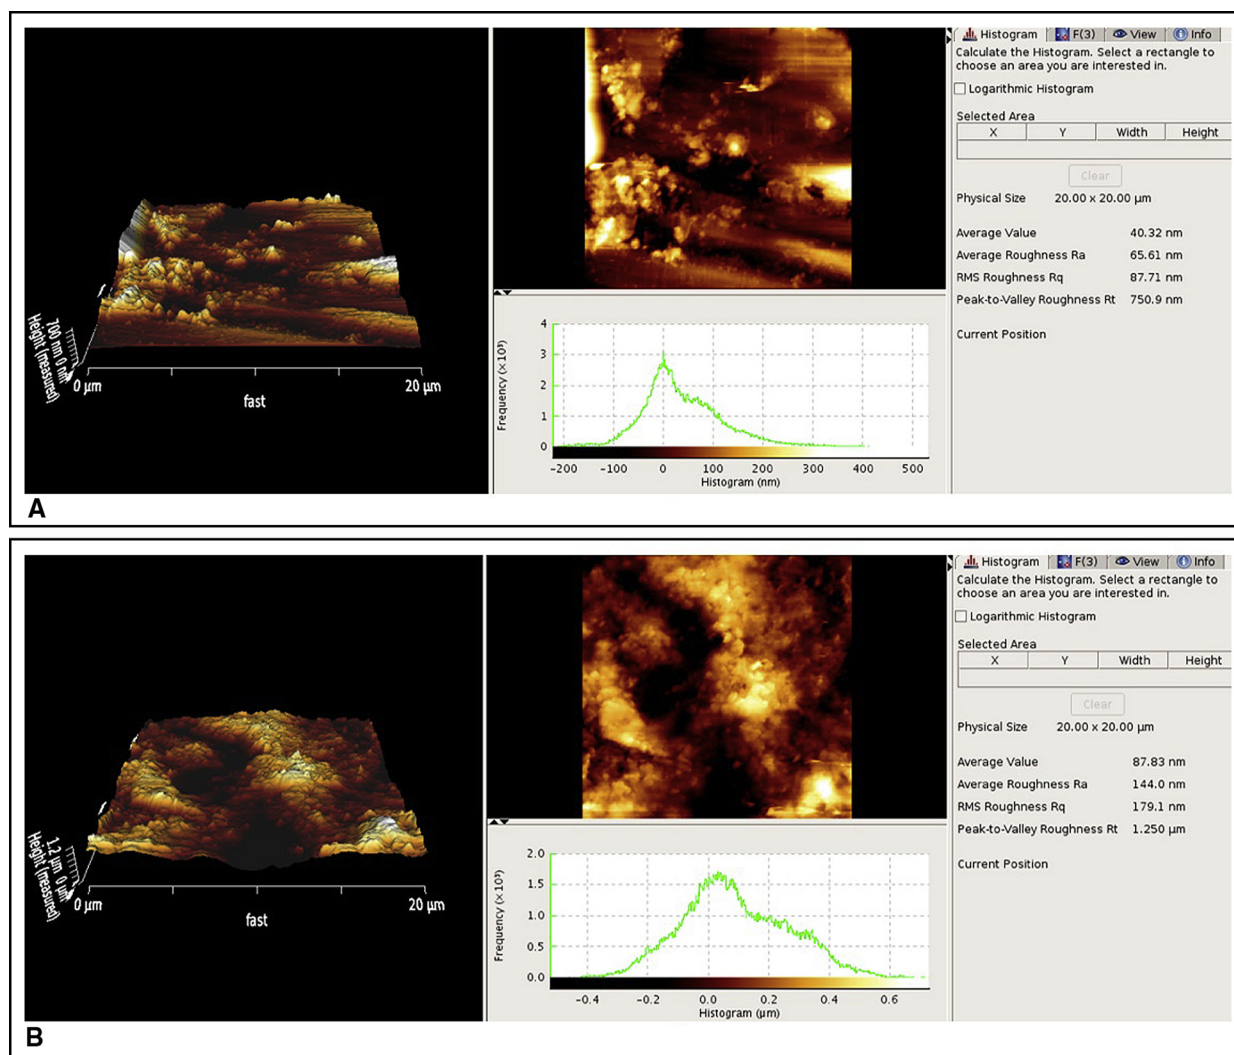

**Fig 3.** Capturing an image from the buccal enamel surface: **A**, before bracket bonding and **B**, after bracket debonding and resin removal using tungsten carbide bur.

Composite resin remnants were completely removed and verified by visual inspection by the operator under a dental operating light.


Different parameters of enamel roughness were determined by AFM (Fig 3): (1) average roughness value (Ra), the arithmetic mean of the height of peaks and the depths of valleys from a mean line in nanometers; (2) root mean square roughness (Rq), the height distribution relative to the mean line in nanometers; and (3) maximum roughness height (Rt), representing the isolated profile features on the surface.

The duration of composite removal was also calculated and statistically analyzed by 1-way analysis of variance (ANOVA) and the Tukey post hoc test. The


level of significance was set at 0.05. Roughness parameters were statistically analyzed by repeated-measures ANOVA. If we had only 1 group in a before-and-after design, we would analyze the data using paired-samples *t* tests. But in this study, we had 2 independent variables including times (before, after) and groups (tungsten carbide, white stone, and tungsten carbide under loupe magnification). To control the type I error of statistical tests, we used repeated-measures ANOVA.

## RESULTS

Composite resin removal increased enamel surface roughness compared with the initial values in all 3

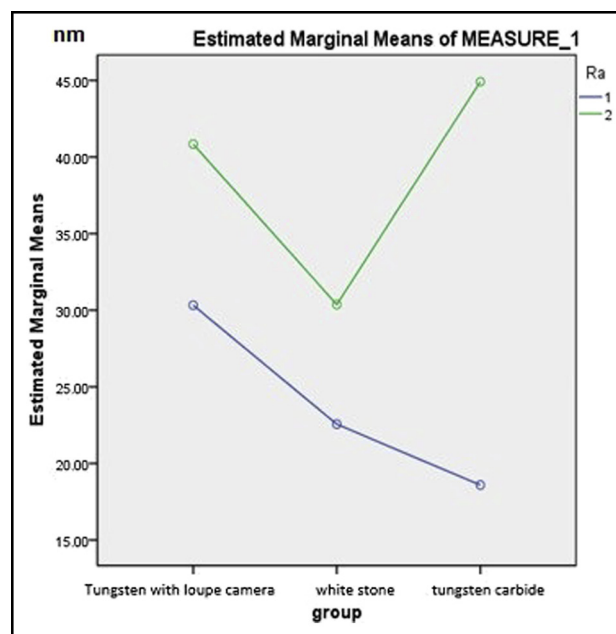

**Fig 4.** Changes in Ra value after use of white stone bur, tungsten carbide, and tungsten carbide bur under loupe magnification before bonding (*line 1*) and after debonding (*line 2*).

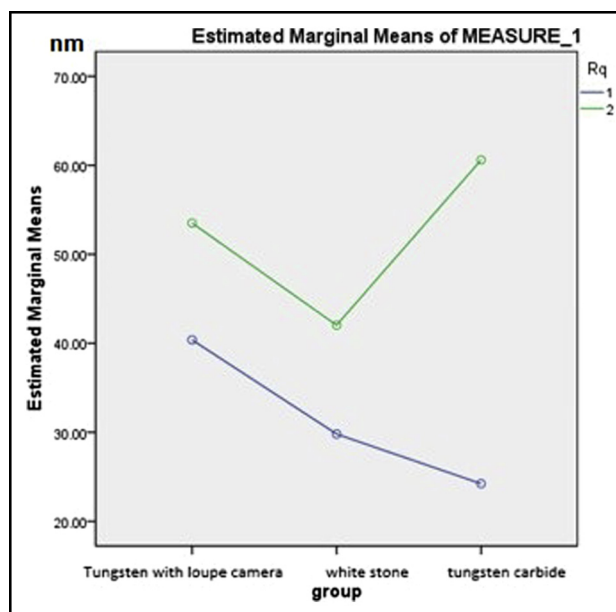


**Fig 5.** Changes in Rq value after use of white stone bur, tungsten carbide bur, and tungsten carbide bur under loupe magnification before bonding (*line 1*) and after debonding (*line 2*).

methods. The Ra, Rq, and Rt values showed significant changes after composite removal in all 3 groups compared with the baseline values ( $P < 0.0001$ ).

No significant differences were noted among the different burs regarding Ra ( $P = 0.9$ ), Rq ( $P = 0.14$ ), and

Rt ( $P = 0.29$ ) after composite resin removal (Figs 4-6, respectively). Number 1 (blue line) in Figures 4 through 6 represents the values before debonding, and number 2 (green line) shows the values after debonding. According to the Tukey post hoc test, the

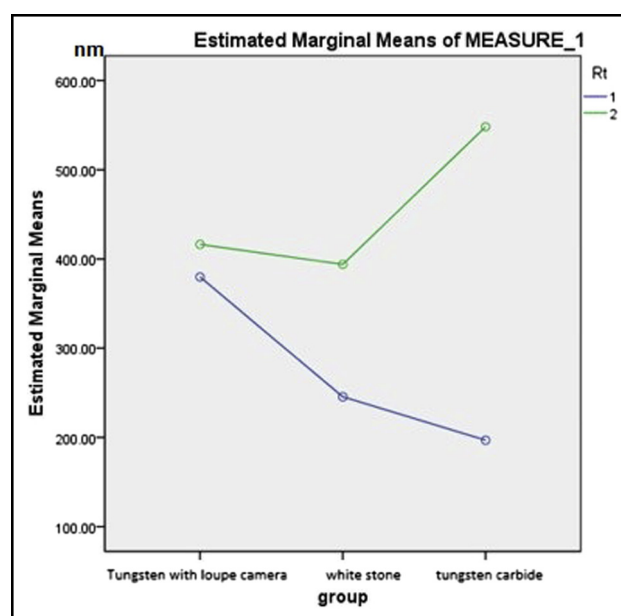

**Fig 6.** Changes in Rt value after use of white stone bur, tungsten carbide bur, and tungsten carbide bur under loupe magnification before bonding (line 1) and after debonding (line 2).

**Table.** Time required (seconds) for resin removal using tungsten carbide bur, white stone bur, and tungsten carbide bur under loupe magnification

Method	Number	Mean $\pm$ SD	95% CI		Minimum	Maximum
			Lower limit	Upper limit		
Tungsten carbide bur under loupe magnification	10	33.6 $\pm$ 7.24	28.42	38.78	23.0	43.0
White stone bur	10	56.5 $\pm$ 10.66	48.98	64.22	42.0	79.0
Tungsten carbide bur	10	34.2 $\pm$ 5.12	30.54	37.86	26.0	40.0

mean values of time required for resin removal with the tungsten carbide bur and tungsten carbide bur under loupe magnification were similar (34.2 and 33.6 seconds, respectively) and were significantly lower than the time for the white stone bur (56.6 seconds; both,  $P < 0.0001$ ; Table). The difference between the tungsten carbide bur and the tungsten carbide bur under loupe magnification was not statistically significant ( $P > 0.05$ ).

## DISCUSSION

Leaving the outermost layer of enamel as intact as possible is the orthodontist's main goal when removing brackets and adhesive remnants.<sup>21</sup> The aim of this study was to compare the enamel surface roughness values after removal of the adhesive using 3 methods as well as the time required to perform this procedure.

Our results showed that regardless of the bur type used, an increase in enamel roughness occurs after resin

removal. Similarly, it has been shown in many studies that irrespective of the method used to remove excess adhesive resin from the enamel surface, scarring of enamel is inevitable.<sup>4,22</sup> Sigilliao et al<sup>23</sup> also reported that all rotary instruments caused various changes in the enamel surface.

Concerning enamel surface roughness, although there were no significant differences among the 3 groups in our study, the white stone created the smoothest surface, and adhesive removal with the tungsten carbide bur resulted in the roughest surface. Therefore, the use of less expensive and more durable white stone burs seems to be economically advantageous in removing adhesive resin remnants after orthodontic debonding. Additionally, the second smoothest enamel surface was obtained using the tungsten carbide bur under loupe magnification. Similarly, Karan et al<sup>2</sup> reported that carbide burs increased enamel roughness, whereas composite burs created less roughness. Gwinnett and Gorelick<sup>24</sup> also indicated that a



green rubber wheel was more effective in leaving a smooth surface and was less destructive to enamel than a tungsten carbide bur. In contrast, Zachrisson and Arthur<sup>25</sup> scored enamel surface after resin removal with green rubber as 3 and with a tungsten carbide bur as 1. The controversy among these studies may be attributed to the different enamel surface assessment methods.

Dental loupes have proven to be practical, user-friendly, and efficient for evaluating enamel surfaces.<sup>26</sup> Their use has been shown to affect the quality of debonding and often causes less enamel damage and leaves fewer resin remnants.

We used AFM to evaluate surface texture. This method has proven to be effective for assessment of microirregularities on hard surfaces. The advantages of AFM include providing 2-dimensional and 3-dimensional images simultaneously and requiring minimal sample preparation. Moreover, it does not require staining or coating of samples.<sup>16,18,27</sup> Classic studies on enamel surface roughness have used scanning electron microscopy as a visual means of evaluating scarring and scratches of the enamel surface caused by different debonding techniques.<sup>12,28</sup> Since scanning electron microscopy cannot provide a quantitative mode of evaluation, this method cannot be used for comparative assessment of enamel roughness.<sup>2</sup> Some studies have assessed the enamel surface 2 dimensionally and have only used the mean roughness value as a surface roughness parameter,<sup>29,30</sup> although Whitehead et al<sup>31</sup> reported that this parameter was inadequate for surface profile registration. Furthermore, Janiszewska-Olszowska et al<sup>32</sup> demonstrated that assessment of the enamel surface damage with scanning electron microscopy was not completely objective.

To determine the exact profile, we used Rq and Rt parameters in addition to Ra. Several studies have used the Ra parameter as the only indicator of surface roughness; however, it had limitations when used alone.<sup>2,12</sup> In spite of increased accuracy of the results by using various parameters related to surface roughness, these results must be interpreted with caution, since the stylus mode used for measuring the surface roughness factors has various features.<sup>31</sup> Similarly, Wennerberg et al<sup>33</sup> stated that 2-dimensional measurements were not sufficient and that an appropriate surface description should include parameters from height and horizontal measurements. The Ra and Rq parameters increased in all 3 groups, although the difference was not statistically significant. Our findings in this regard agree with those of Ahrari et al.<sup>3</sup> The difference in the cutting efficiency of the burs used in our study may be explained by a number of parameters including the bur

rotation speed, the pressure against the enamel, and the bur type.<sup>12</sup>

In spite of similarity in the enamel surface roughness after resin removal with the mentioned methods, the time required for adhesive removal showed significant differences among the groups mainly due to differences in the cutting efficacy of the instruments, determined by the speed of rotation, bur type, and number of blades.<sup>9,32</sup> The tungsten carbide bur and the tungsten carbide bur under loupe magnification required less time for resin removal than did the white stone bur. Consistently, Ulusoy<sup>8</sup> claimed that a 30-blade tungsten carbide bur was the least time-consuming procedure for removing adhesive remnants. Karan et al<sup>2</sup> also reported that the time required for resin removal with the composite bur was significantly greater than the time required with the carbide bur.

Rough surfaces in the oral cavity result in bacterial plaque adhesion and stain formation. Thus, reduction of surface roughness will lead to a considerable decrease in staining and plaque formation and maturation.<sup>2</sup> According to our results, adhesive removal with a white stone bur creates a smoother surface compared with the tungsten carbide bur, although the difference was not significant. To save time and expedite adhesive removal, resin remnants can be removed with a tungsten carbide bur.

## CONCLUSIONS

Tungsten carbide burs, white stone burs, and tungsten carbide burs under loupe magnification had relatively similar effects on the enamel surface roughness. However, in view of the time required for composite removal with the white stone bur and the cost of purchasing a dental loupe, we still recommend the tungsten carbide bur as the method of choice for removing adhesive remnants after orthodontic bracket debonding.

## REFERENCES

1. Campbell PM. Enamel surfaces after orthodontic bracket debonding. *Angle Orthod* 1995;65:103-10.
2. Karan S, Kircelli BH, Tasdelen B. Enamel surface roughness after debonding. *Angle Orthod* 2010;80:1081-8.
3. Ahrari F, Akbari M, Akbari J, Dabiri GH. Enamel surface roughness after debonding of orthodontic brackets and various clean-up techniques. *J Dent (Tehran)* 2013;10:82-93.
4. Pont HB, Ozcan M, Bagis B, Ren Y. Loss of surface enamel after bracket debonding: an in-vivo and ex-vivo evaluation. *Am J Orthod Dentofacial Orthop* 2010;138:387.e1-9.
5. Zarinnia K, Eid NM, Kehoe MJ. The effect of different debonding techniques on the enamel surface: an in vitro qualitative study. *Am J Orthod Dentofacial Orthop* 1995;108:284-93.
6. Cochrane NJ, Ratnesar S, Reynolds EC. Effect of different orthodontic adhesive removal techniques on sound, demineralized and remineralized enamel. *Aust Dent J* 2012;57:365-72.

7. Vidor MM, Felix RP, Marchioro EM, Hahn L. Enamel surface evaluation after bracket debonding and different resin removal methods. *Dental Press J Orthod* 2015;20:61-7.
8. Ulusoy C. Comparison of finishing and polishing systems for residual resin removal after debonding. *J Appl Oral Sci* 2009;17:209-15.
9. Radlanski RJ. A new carbide finishing bur for bracket debonding. *J Orofac Orthop* 2001;62:296-304.
10. Maciesky K, Rocha R, Locks A, Ribeiro GU. Effects evaluation of remaining resin removal (three modes) on enamel surface after bracket debonding. *Dental Press J Orthod* 2011;16:146-54.
11. Faria-Junior EM, Guirardo RD, Berger SB, Corrêa AB, Corrêa-Sobrinho L, Contreras EF, et al. In-vivo evaluation of the surface roughness and morphology of enamel after bracket removal and polishing by different techniques. *Am J Orthod Dentofacial Orthop* 2015;147:324-9.
12. Eliades T, Gioka C, Eliades G, Makou M. Enamel surface roughness following debonding using two resin grinding methods. *Eur J Orthod* 2004;26:333-8.
13. Hashimoto Y, Hashimoto Y, Nishiura A, Matsumoto N. Atomic force microscopy observation of enamel surfaces treated with self-etching primer. *Dent Mater J* 2013;32:181-8.
14. Winchester L, Orth M. Direct orthodontic bonding to porcelain: an in-vitro study. *Br J Orthod* 1991;18:299-308.
15. Binning G, Quate CF, Gerber C. Atomic force microscope. *Phys Rev Lett* 1986;56:930-3.
16. Kakaboura A, Fragouli M, Rahiotis C, Silikas N. Evaluation of surface characteristics of dental composites using profilometry, scanning electron, atomic force microscopy and gloss-meter. *J Mater Sci Mater Med* 2007;18:155-63.
17. Karan S, Toroglu MS. Porcelain refinishing with two different polishing systems after orthodontic debonding. *Angle Orthod* 2008;78:947-53.
18. Tholt de Vasconcellos B, Miranda-Junior WG, Prioli R, Thompson J, Oda M. Surface roughness in ceramics with different finishing techniques using atomic force microscope and profilometer. *Oper Dent* 2006;31:442-9.
19. Baumann DF, Brauchli L, van Waas H. The influence of dental loupes on the quality of adhesive removal in orthodontic debonding. *J Orofac Orthop* 2011;72:125-32.
20. Jaffer S, Oesterle LJ, Newman SM. Storage media effect on bond strength of orthodontic brackets. *Am J Orthod Dentofacial Orthop* 2009;136:83-6.
21. Ogaard B. Oral microbiological changes, long term enamel alterations due to decalcification and caries prophylactic aspects. In: Brantley WA, Eliades T, editors. *Orthodontic materials: scientific and clinical aspects*. Stuttgart, Germany: Thieme; 2001. p. 124-39.
22. Ozer T, Basaran G, Kama J. Surface roughness of the restored enamel after orthodontic treatment. *Am J Orthod Dentofacial Orthop* 2010;137:368-74.
23. Sigilliao LC, Markezan M, Elias CN, Ruellas AC, Sant' Anna EF. Efficiency of different protocols for enamel clean-up after bracket debonding: an in vitro study. *Dental Press J Orthod* 2015;20:78-85.
24. Gwinnett AJ, Gorelick L. Microscope evaluation of enamel after debonding: clinical application. *Am J Orthod* 1977;71:651-65.
25. Zachrisson BU, Arthun J. Enamel surface appearance after various debonding techniques. *Am J Orthod* 1979;75:121-37.
26. Kitahara-Céia FM, Mucha JN, Marques dos Santos PA. Assessment of enamel damage after removal of ceramic brackets. *Am J Orthod Dentofacial Orthop* 2008;134:548-55.
27. Marshall GW Jr, Balooch M, Gallagher RR, Gansky SA, Marshall SJ. Mechanical properties of the dentinoenamel junction: AFM studies of nanohardness, elastic modulus and fracture. *J Biomed Mater Res* 2001;4:87-95.
28. Piacentini C, Sfondrini G. A scanning electron microscopy comparison of enamel polishing methods after air-rotor stripping. *Am J Orthod Dentofacial Orthop* 1996;109:57-63.
29. Ayad MF, Rosenstiel SF, Hassan MM. Surface roughness of dentin after tooth preparation with different rotary instrumentation. *J Prosthet Dent* 1996;75:122-8.
30. Wahle JJ, Wendt SL. Dentinal surface roughness: a comparison of tooth preparation techniques. *J Prosthet Dent* 1993;69:1160-4.
31. Whitehead SA, Shearer AC, Watts DC, Wilson NH. Comparison of two stylus methods for measuring surface texture. *Dent Mater* 1999;15:79-86.
32. Janiszewska-Olszowska J, Szatkiewicz T, Tomkowski R, Tandecka K, Grocholewicz K. Effect of orthodontic debonding and adhesive removal on the enamel—current knowledge and future perspectives—a systematic review. *Med Sci Monit* 2014;20:1991-2001.
33. Wennerberg A, Sawase T, Kultje C. The influence of Carisolv on enamel and dentine surface topography. *Eur J Oral Sci* 1999;107:297-306.